



ISSN: 2320-8090

Available online at <http://www.journalijcst.com>

International Journal of Current Science and Technology
Vol.3, Issue, 12, pp. 178-182, December, 2015

IJCST

RESEARCH ARTICLE

INVESTIGATION FOR OPTIMAL INHIBITION EFFICIENCY AGAINST MILD-CARBON STEEL CORRRSION IN 0.1M ACIDIC MEDIA USING CASHEW EXTRACT

Olawale. O*,¹ Akinmoladun A.I.,² Oyawale. F.A,³ Bello, J.O. and Neil Phillip⁴

³Department Landmark University Omu-Aran Kwara State Nigeria

¹Department of Physics and Technology Bronx Community College of the University of New York

²Department Covenant University Otta Nigeria

ARTICLE INFO

Article History:

Received 15th September, 2015

Received in revised form 21st October, 2015

Accepted 06th November, 2015

Published online 28st December, 2015

Key words:

Corrosion, HCl, H₂SO₄, Inhibition,
Mild Carbon steel.

ABSTRACT

Corrosion is an everyday challenge in all sectors of the economy particularly the manufacturing industry and this has led to massive economic loss. Literature is sparse on optimal Inhibition efficiency from Hydrochloric acid (HCl) and Tetra-oxo-sulphate (vi) Acid (H₂SO₄). The aim and objective of this research is to observe optimal Inhibition Efficiency from acidic media using cashew extracts as eco-friendly corrosion inhibitor. 0.1M of HCl and H₂SO₄ of 0.1M were used for the cashew extract in this research. Mild carbon steel with thickness 0.1 cm was used. It was cut into various coupons of dimensions 4 x 5 x 0.1 cm. The cashew waste extract produced was used as a corrosion inhibitor on mild carbon steel in 0.1M of HCl and H₂SO₄. It was observed that as the concentration of inhibitor increases, the inhibitor efficiency also increases. The optimal inhibition efficiency observed in HCl was 80.5% while 83.7% was in H₂SO₄. After 336 hours of test, it was concluded that H₂SO₄ is a better acidic medium.

Copyright © 2015 Akinmoladun A.I et al., This is an open access article distributed under the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

INTRODUCTION

Corrosion is the gradual deterioration of a material by electrochemical reaction due to its interaction with its environment. It has been an everyday challenge in all sectors of the economy particularly the manufacturing industry (El-Etre, 2003). A number of ways such as material selection, cathodic or anodic protection, coatings and the use of corrosion inhibitors had been used to reduce corrosion in industries (Lebrini et al.2011; Yahazri et al.2011). Carbon steel is one of the most important alloys being used in a wide range of industrial applications. There are several ways of tackling the issue of corrosion in the industry and one of such ways is the use of inhibitors which is eco-friendly. According to Shanableh (2011); the use of inhibitors had been promising, inexpensive and effective. It was observed that the natural inhibitors could potentially serve as an effective substance for corrosion inhibitors without constituting risk for human health and environment in which people live in. Naturally occurring molecules exhibiting a strong affinity for metal surfaces are the focus of research oriented toward the development of environmentally friendly corrosion inhibitors; compounds showing good inhibition efficiency and low environmental risk. Many researchers have done some works on green corrosion using grape pomace (Rocha et al. 2012), apricot juice and Spirulina platensis (Okafor et al.2011, Aboia and James, 2011). Among the so-called "green corrosion inhibitors" are organic compounds that act by adsorption on the metal surface, such as ascorbic acid, succinic acid, try-

ptamine, caffeine and extracts of natural substances (Eddy et al. 2009).The efficiency of these organic corrosion inhibitors is related to the presence of polar functional groups with S, O or N atoms in the molecule, heterocyclic compounds and pi electrons. The polar function is usually regarded as the reaction center for the establishment of the adsorption process. Studies have been conducted on natural extracts that can significantly replace synthetic compounds. One of these natural compounds is fruit (Antonijevic, et al.2008).Fruit is a rich source of chemicals such as vitamins, minerals, and phenolic compounds. According to Rocha et al (2012), banana peel, fruit peel (mango, orange and passion fruit), coffee grounds, papaya seed, seeds and peels from papaya and garlic produced inhibitors. The use of industrial wastes as corrosion inhibitors is indeed welcoming and very appealing. Many studies had been carried out to find suitable compounds useful as corrosion inhibitors for metal in different aqueous solutions (Rajendra, et al.2005). Juice and seed extracts of cantaloupe acted as good natural inhibitor for corrosion of cast iron in 0.1M HCl solution (Khadijah et al. 2015). According to Salami et al.2012; as the concentration of inhibitor produced increases, the corrosion rate decreases. Furthermore, their findings showed that the inhibitor had an optimum efficiency of about 71 % when Musa Sapiantum peels extract was used as corrosion inhibitor. The aim and objective of this research is to observe optimal Inhibition Efficiency from acidic media of 0.1M for mild carbon steel using cashew extract as an eco-friendly inhibitor.

*Corresponding author: Akinmoladun A.I Sheila Dhar Institute of Soil Science, Department of Chemistry, University of Allahabad, Allahabad, India

METHODOLOGY

MATERIALS

- i. Waste fruits of cashew (*Anacardium occidentale L.*) were collected
- ii. Mild carbon Steel

Chemicals

All the chemical and reagent used in this work were of analytical grade. They include: Hydrochloric Acid; Sulphuric Acid; Acetone and Ethanol

Methodology

Preparation of samples

The samples prepared here are the corrosion medium for the mild steel bar needed in calculating the weight loss of the material. The samples are 1M of HCl and 0.1M of H₂SO₄.

The electrolytes 0.1 molL⁻¹ HCl and 0.1 molL⁻¹ were solution prepared using double-distilled water. All chemicals were of analytical-grade. The experiments were carried out under non-stirred and naturally aerated conditions.

Preparation of plant extract

The 2kg of waste cashew fruits were sun dried. After sun drying them the cashew nut was separated from the dried waste fruits; then pulverized. 150g of the ground dried waste cashew powder was weighed and soaked in 250 ml of ethanol for 24 hours, and then filtered and concentrated using rotary evaporator and water bath. The resulting extract was in semi-solid form.

Preparation of Specimen

Carbon steel strips (BDH grade) containing (weight %): C 0.2, P 0.024, Si 0.003, Mn 0.35, and rest Fe were used in this research. Coupons cut with 4 x 5 x 0.1 cm dimensions were used for weight loss measurements. 10 mild steel bars of this dimension were cut and where used for this test. These coupons were cleaned by distilled water and ethanol. These coupons were further treated using emery paper. Then, washed using distilled water and degreased with acetone and later stored in the desiccator.

Weight Loss Measurements

Weight loss measurements were conducted under total immersion using 250 ml capacity beakers containing 20-100% test solution at 30-33°C maintained in the laboratory (room temperature). The carbon steel coupons were weighed and suspended in the beaker with the help of rod and hook. For the effect of temperature on the inhibition efficiencies, all the tests were carried out in the temperature range of 30-33°C.

Procedure

The mild carbon steel specimens was immersed in 100mL of 0.1M HCl and 0.1M H₂SO₄ containing various concentrations of the inhibitor (20%, 40%, 60%, 80%) in the presence and absence of the corrosion inhibitor for 336 hours. First, there were two control experiments for HCl and H₂SO₄. Then various percentages of the inhibitor were added to the other beakers containing the various test samples. The specimens were totally immersed in all ten (10) test solutions and were left for 336 hours during which readings were carried out at intervals of 48 hours. 7 readings were carried out and the results recorded accordingly. The weight of the specimens before and after immersion was determined after every 48 hours using weighing balance. The corrosion products were cleansed with distilled water, dried and then weighed to determine the weights. The inhibition efficiency (IE) was calculated using the following equation.

$$\frac{(V_0 - V_1)}{V_0} \dots\dots 1$$

Where V₀ is the corrosion rate in the absence of the inhibitor, and V₁ is the corrosion rate in the presence of the inhibitor.

Surface Examination

For morphological study, surface features (2.0 cm x 2.0 cm x 0.15 cm) of carbon steel were examined before and after exposure to 0.1M HCl and 0.1M H₂SO₄ solutions for 336 hour with was used in examining the control experiment of HCl and H₂SO₄ and that of the optimum corrosion inhibitor in both acids.

RESULTS AND DISCUSSION

Weight Loss Method

The corrosion of mild steel in 0.1M HCl and 0.1M H₂SO₄ solution containing various concentrations of inhibitor at room temperature was studied by weight loss measurements. The corrosion rate of mild steel was determined via the below formula.

$$V = (W_2 - W_1) / (A t) \quad (1) \text{ where:}$$

W₁ = initial weight (prior to immersion) W₂ = final weight (after immersion) A = surface area of the sampel
t = exposure time Furthermore, the inhibition efficiency (IE) of each sample was calculated by using equation 2 .

$$IE = (V_0 - V_1) / V_0 \quad (2)$$

V₀ = corrosion rate without inhibitor V₁ = corrosion rate with the addition of inhibitor

$$W = \frac{\Delta M}{St} \dots\dots\dots 2$$

Where m is the mass loss (g)
S = 20cm² = 0.002m² [the area (cm²)]
t = 48hours [immersion period (hours)]
The percentage inhibition efficiency [IE%] was calculated

using the relationship.

$$\left(\frac{V_0 - V_1}{V_0}\right) \times 100\% \dots\dots\dots 3$$

Where V_0 is the corrosion rate in the absence of the inhibitor, and V_1 is the corrosion rate in the presence of the inhibitor.

Table 1 Corrosion rates data of mild steel in 0.1M HCl in absence and presence of different concentrations of cashew inhibitor.

Inhibition concentration (%)	Corrosion rates (g/m ² .hr)		IE (%)
0	0.69	0.207	20.7%
40	0.52	0.402	40.2%
60	0.35	0.598	59.8%
80	0.17	0.805	80.5%

Table 2 Corrosion rates data of mild steel in 0.1M H₂SO₄ in absence and presence of different concentrations of cashew inhibitor.

Inhibition concentration (%)	Corrosion rates (g/m ² .hr)		IE (%)
0	1.04		
20	0.69	0.337	33.7%
40	0.52	0.5	50%
60	0.35	0.663	66.3%
80	0.17	0.837	83.7%

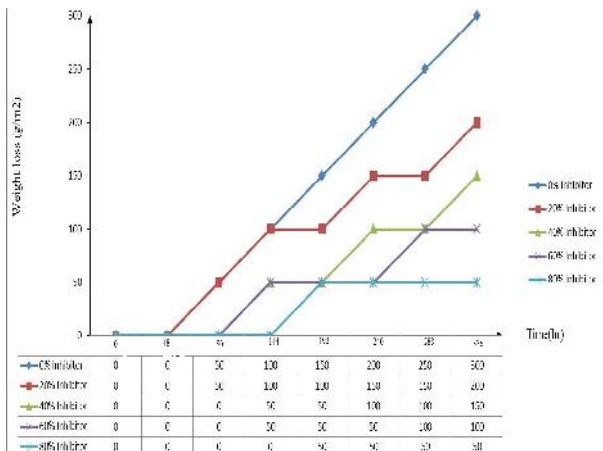


Figure 1 Weight loss-time curves of carbon steel in 0.1M H₂SO₄ in the absence and presence of different concentrations of Cashew inhibitor.

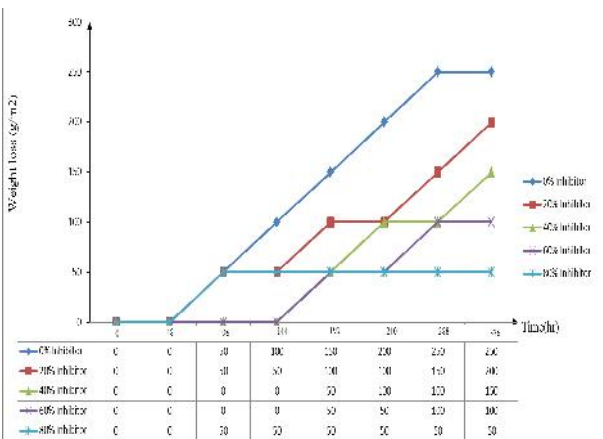


Figure.2 Weight loss-time curves of carbon steel in 0.1M HCl in the absence and presence of different concentrations of Cashew inhibitor

Surface Morphology Result

FT-IR was used to evaluate the nature of the film formed on the surface of the metal. After the concentration of the inhibitor with the highest Inhibition Efficiency (IE %) was discovered, the samples were sent to the laboratory for analysis. Figures 1-3 showed the analysis done on the metal with 0% inhibition concentration and that of 80% inhibition concentration in both 0.1M HCl and 0.1M H₂SO₄.

The strong band at approximately 3450cm⁻¹ can be associated with O–H stretching of the phenolic group. The band at 2928 cm⁻¹ is related to C–H stretching vibration. The strong band at 1630 cm⁻¹ is assigned to conjugated C=O stretching vibration. The band at 1552 cm⁻¹ can be attributed to C=C-C aromatic ring stretching. The bands between 1467 and 1431 cm⁻¹ can be attributed to angular deformations of C-O-H in phenols. The band at approximately 1321 cm⁻¹ is attributed to C-O stretching from the pyran-derived ring structure present in the flavonoids. The bands at 1083 and 1151cm⁻¹ can be assigned to C-H deformations of the aromatic ring. This result indicates that cashew extract contain flavonoids in their composition, which can act as corrosion inhibitors. The FT-IR spectra for figures 4 and 5 are almost the same, so it can be concluded that the extracts have the same composition, and differ mainly on their concentration

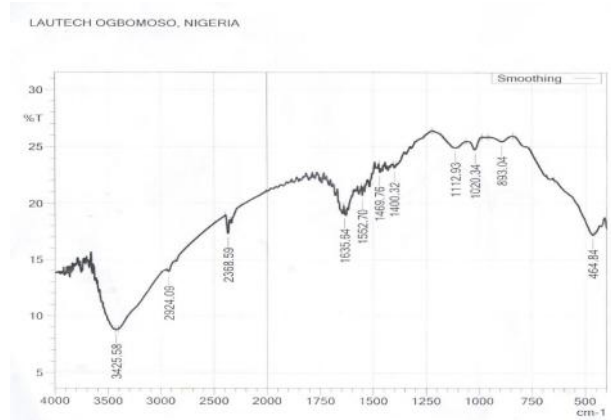


Figure 3 FT-IR spectra of coupon with 0% inhibition concentration in 0.1M HCl

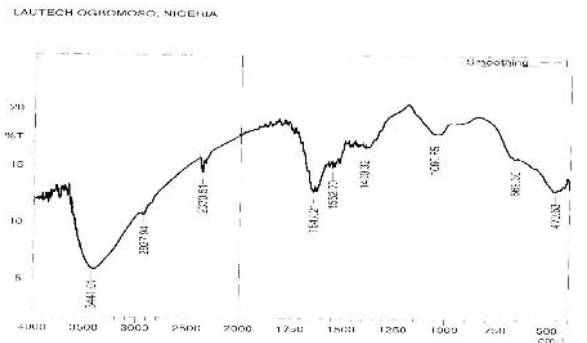


Figure 4 FT-IR spectra of coupon with 80% inhibition concentration in 0.1M HCl

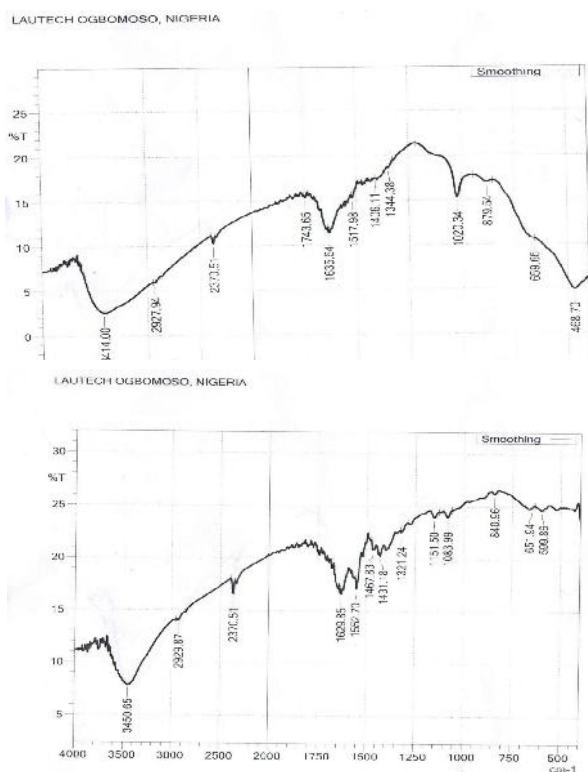


Figure 6 FT-IR spectra of coupon with 80% inhibition concentration in 0.1M H₂SO₄

Scanning electron microscopy (SEM)

Surface morphology of polished mild steel, mild steel immersed in 0.1M HCl, mild steel immersed in 0.1M H₂SO₄, mild steel immersed in 0.1M HCl with 80% corrosion inhibitor and mild steel immersed in 0.1M H₂SO₄ with 80% corrosion inhibitor were recorded and depicted in Figures .7(a) – (e).

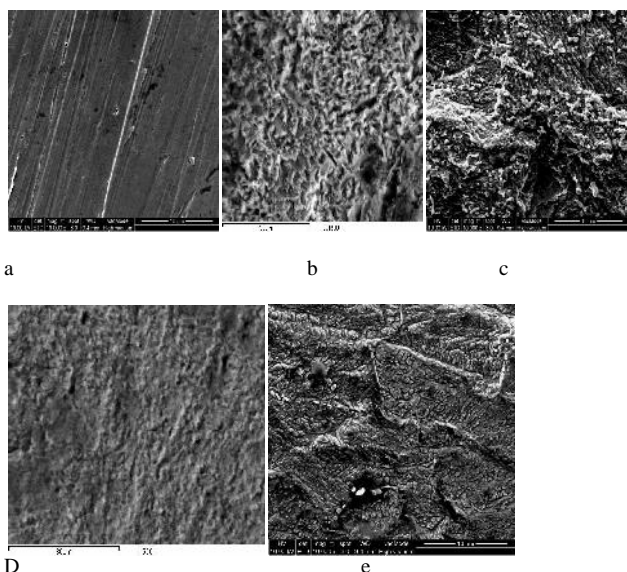


Figure 7 SEM micrographs of mild carbon steel surface (a) before immersion (b) total immersion in 0.1M HCl (c) total immersion in H₂SO₄ (d) immersion in 0.1M HCl with 80% inhibition concentration (e) immersion in 0.1M H₂SO₄ with 80% inhibition concentration.

DISCUSSION OF RESULTS

From the above, it was observed that the inhibition concentration of 80% for both 0.1M HCl and 0.1M H₂SO₄ gave the highest inhibition efficiency i.e. 80.5% and 83.7% respectively. From Figures 1-2, the graphs clearly showed that weight loss reduced as more concentrations of the corrosion inhibitor was added. Within the test hours of 336 hours, there was a 300 and 250g/m² of weight loss in both 0.1M HCl and 0.1M H₂SO₄ with 0% inhibition concentration, while there was just a 50g/m² of weight loss both 0.1M HCl and 0.1M H₂SO₄. The inhibition efficiency is directly proportional to the concentration of the inhibitor (i.e. inhibition efficiency increases with increased inhibition concentration). It was observed from the FT-IR result that the cashew extract contains flavonoids in their composition, which can act as corrosion inhibitors.

CONCLUSION

It was concluded that cashew waste extract was a very good eco-friendly corrosion inhibitor for mild carbon steel. At 80% concentration of the inhibitor, it was discovered that the inhibition efficiency was highest in both media at 80.5% for HCl and 83.7% for H₂SO₄. Furthermore, as the concentration of the inhibitor increases, the corrosion rate decreases and the inhibitor has an optimum efficiency of 83.7%. The result obtained from the FT-IR spectra showed flavonoids which are the active corrosion inhibiting agents in the cashew. SEM analysis showed a better passive layer against the corrosive ions on the surface of the mild steel in H₂SO₄ than in HCl. This showed that H₂SO₄ was a better corrosion inhibitor.

References

- i. Aboia O.K., James A.O., (2010) "The effects Of Aloe vera extract on Corrosion and Kinetics of Corrosion process of zinc in HCl Solution", Corrosion Science 52(2): 661-664.
- ii. Antonijevic M.M and Petrovic M.B (2008). "Copper Corrosion Inhibitors. A Review". Int. J. Electrochem. Sci. 3:1.
- iii. Eddy N.O., Odoemelam S.A.(2009) "Inhibition of corrosion of mild steel in acidic medium using ethanol extract of Aloe vera", Pigment and Resin Tech.38(2):111-115.
- iv. El-Etre AY (2003). Inhibition of aluminum corrosion using Opuntia extract. Corr. Sci. 4(5):2485–2495.
- v. Khadijah, M.E; Arwa, O; Al-Ahmadi, Bayan, A; Torjoman Najila, M.M and Sara, N.S. (2015) Corrosion and corrosion Inhibitor of Cast Iron in Hydrochloric Acid Solution by Cantaloupe (Cucumis melon) as Green Inhibitor. Afr. J. Pur & Appl. Chem. 9(3):39-49. Doi: 10.5899/SJPAC20150607. ISSN: 1996-0840.
- vi. Lebrini, M; Robert, F; and Ross, C. (2011) Alkaloids Extract from Palicourea guianensis Plant as Corrosion of C38 Steel in 1 M Hydrochloric Acid Medium. Int. J. Electrochem. Sci: 6: 847-859.
- vii. Okafor, P.C, Ebenso, E.E, Ekbe, U.J (2010)

- Azadirachta Indica Extract as Corrosion Inhibitor for Mild Steel in Acidic Medium, *Inter. J. Electrochem. Sci.*:114-122
- viii. 8. Rajendran, S., Ganga, S.V., Arockiaselvi, J. and Amalraj, A.J. (2005): Corrosion Inhibition by Plant Extracts – An Overview. *Bulletin of Electrochem*: 21: 367-377.
- ix. Rocha J.C, Gomes J.A, Elia E.D, Cruz A.P, Cabral L.M, Torres A.G and Monteiro M.V (2012). Grape Pomace extracts as green corrosion inhibitors for carbon steel in hydrochloric acid solutions. *Int. J. Electrochem. Sci.* 7(12):11941-11956.
- x. 9. Salami, L; Were, T.O.Y; Akinyemi, O.P and Patinvo, R.J (2012) A Study of the Corrosion Inhibitor of Mild Steel in Sulphuric Acid using Musa Sapientum Peels Extract. *Glob. Engr. & Techn. Rev*: 2(12):1-6.
- xi. 10. Shanableh, A. (2011) Studies on Natural Extracts as Inhibitors of Mild Steel Corrosion in 1M HCl Solution. Master Thesis, American University of Sharjah. Sharjah, UAE
- xii. 11. Umoru L.E; Fawehinmi, A and Fasasi, A.Y (2006) Investigation of the Inhibitive Influence of Theobroma Cacao and Cola Acuminata Leaves Extracts on the Corrosion of a Mild Steel in Sea Water. *J. Applied Sci. Res*: 2 (4), 299-304.
- xiii. 12. Yuhazri, M.Y; Jeeferie, A.R; Haeryip S; Noorirah, O. and Warikh, A.R (2011). *International Journal of Applied Science and Technology*. 2011b Vol.1, Iss.1. pp.45-49.