

# Hydration Characteristics of Bagasse in Cement-Bonded Composites

Omoniyi T. E\*, Akinyemi B. A

Department of Agricultural and Environmental Engineering, University of Ibadan, Oyo State, Nigeria

**Abstract** Four compatibility assessment methods were used to ascertain the compatibility of bagasse with cement composite. The time to reach maximum hydration temperature was achieved when  $\text{CaCl}_2$  and water above  $60^\circ\text{C}$  were used as treatment agents. Maximum hydration temperature between  $55^\circ\text{C}$  –  $61^\circ\text{C}$  were achieved when treated with 1 – 3%  $\text{CaCl}_2$ . The inhibitory index value of 1.58% - 8.83% were achieved when treated with bagasse while others have value greater than the acceptable parameter standard for exterior use. The maximum hydration rate of 4.0 was achieved when the bagasse fiber was treated with 3%  $\text{CaCl}_2$  and this was closely followed by 2%  $\text{CaCl}_2$  at 3.38. These results showed that all the different compatibility assessment parameters adopted indicated that bagasse was incompatible with Portland cement without pre-treatment. Treatment of bagasse with cold water and addition of 2%  $\text{CaCl}_2$  satisfied all requirements for compatibility in terms of time to reach maximum temperature, the maximum hydration temperature and the inhibitory index value. Treatment with  $\text{CaCl}_2$  gave the best result probably due to its capacity to minimize the adverse effect of the soluble sugars and extractives and also to accelerate cement hardening and setting. This result shows that treated bagasse is compatible with cement bonded composite for construction purposes.

**Keywords** Hydration Index, Bagasse, Treatment, Temperature, Time

## 1. Introduction

Increasing attention should be given to the use of natural fibre with a view to conserving energy and protecting the environment and because of basic engineering properties of crack resistance, ductility and energy absorption that it impacts on cement particleboard (CPB). In the past, wood was the main aggregate employed in CPB. However economic and environmental pressures have led to other lignocelluloses being considered for use. A range of substitute materials, such as agricultural and wood processing residues, tree barks and weeds, has been tested. Examples include rice straw and giant ipil-ipil, oil palm shell and cork granules[1]. Several other candidates are available, including rattan cane, coconut husk, banana, bagasse, bamboo, and oil palm. These materials are available in abundance and present as waste in West Africa. Natural fibres cement composite is useful because of eco-friendly nature and provide the most economic and socially useful outlet for natural fibre chips, residues and agricultural wastes. Coconut is one of the most economically useful palms in tropical Asia and Africa[2]. All parts of the palm are useful and local people use it for lumber and as source of food.

Coconut husk however is of limited commercial use at present.

Rattan, a non timber forest product used for manufacturing cane furniture, grows as a spiny climber in the tropics and sub-tropics. Following harvesting, rattan is stripped of its spines and leaf sheaths before drying. Unfortunately much of the cane material becomes discoloured by staining fungi during this part of the process[1]. This material cannot be processed for furniture and is considered waste. At present 20 – 30 % of the processed rattan is waste.

The major challenges facing the development of durable natural fibre cement composite are the inherent weakness of the natural fibre particles themselves such as low elastic modulus, high water absorption, susceptibility to fungal and insect attack and lack of durability in alkaline environment. And also because of the influence of botanical components (hemi-cellulose, starch, tannin, phenols, and lignin) all which are known to inhibit the normal setting and strength development properties of cement matrix. This work examines the compatibility of bagasse with ordinary Portland cement using hydration tests.

## 2. Materials and Methods

The hydration test method used was the same as described by[3] and[4]. This test investigated the suitability of bagasse in wood-cement manufacture. Bagasse was hammer-milled,

\* Corresponding author:

temidayoomoniyi@gmail.com (Omoniyi T. E)

Published online at <http://journal.sapub.org/cmaterials>

Copyright © 2013 Scientific & Academic Publishing. All Rights Reserved

sieved and dried for two weeks. Only particles that passed through 850  $\mu\text{m}$  sieve and retained on a 600  $\mu\text{m}$  were used. The bagasse/water/cement mixtures comprised 15 g bagasse particles, 200 g ordinary Portland cement and 90.5 ml distilled water (as in [5] and [2]). Each 15g bagasse sample was gradually mixed with 200g of cement in a polythene bag thereafter distilled water was added to the mixture and stirred until homogenous paste was obtained. Required quantity of  $\text{CaCl}_2$  (at four concentrations by weight 0, 1, 2, and 3% respectively) were added to the paste. The mixture was transferred to a Dewar flask and a thermocouple was inserted to enable temperature measurement at 1 – min intervals over a 23 – h period. The time taken to attain maximum temperature was assessed. Three replicates were used. The experiments were carried out at room temperature of  $25 \pm 2^\circ\text{C}$ . The same procedure was followed for bagasse pre-treated with cold and hot water.

To calculate the inhibitory index (I), the following equation was used:

$$I = \left( \left( \frac{t_2 - t_2'}{t_2'} \right) \times \left( \frac{T_2' - T_2}{T_2'} \right) \times \left( \frac{S_2' - S_2}{S_2'} \right) \right) \times 100 [6]$$

Where:

$t_2$  is the time to reach maximum temperature of the inhibited cement (bagasse-cement-water mixture)

$t_2'$  is the time to reach maximum temperature of the uninhibited cement (cement-water mixture)

$T_2$  is the maximum hydration temperature of the inhibited cement (bagasse-cement-water mixture)

$T_2'$  is the maximum hydration temperature of the uninhibited cement (cement-water mixture)

$S_2$  is the maximum temperature – time slope of the inhibited cement (bagasse-cement-water mixture)

$S_2'$  is the maximum temperature – time slope of the uninhibited cement (cement-water mixture).

### 3. Results and Discussion

#### 3.1. Hydration Test Results

##### 3.1.1. Time Taken by the Bagasse-Cement to Attain Maximum Temperature

**Table 1.** Influence of Treatments on the Hydration Behaviour of the Bagasse-Cement Composite

Particle/Cement Mixture	Parameters				Levels of compatibility			
	t(h)	T <sub>max</sub>	I (%)	R	Ct	CT <sub>max</sub>	CI	CR
Untreated Bagasse	18	40	47.5	0.56	U	U	MI	L
Bagasse and Cold Water	14	47	30.2	1.2	S	U	MI	L
Bagasse + Water at 50 <sup>0</sup> C	13	48	25.17	1.38	S	U	MI	L
Bagasse + Water at 60 <sup>0</sup> C	12	48	21.57	1.5	S	U	MI	L
Bagasse + Water at 70 <sup>0</sup> C	12	48	19.39	1.5	S	U	MI	L
Bagasse + Water at 80 <sup>0</sup> C	11	49	17.04	1.73	S	U	MI	L
Bagasse + 1% $\text{CaCl}_2$	10	55	8.83	2.5	S	IS	C	M
<b>Bagasse + 2% <math>\text{CaCl}_2</math></b>	<b>8</b>	<b>61</b>	<b>1.58</b>	<b>3.88</b>	<b>S</b>	<b>S</b>	<b>C</b>	<b>H</b>
Bagasse + 3% $\text{CaCl}_2$	7	58	1.98	4.0	S	IS	C	H
Clean Cement Paste	6	66						
Cement and Sand	7	63						

The effects of pre-treatments on the hydration behaviour of the bagasse-cement are presented in Table 1. It took the

untreated bagasse-cement mixture about 18 hours to attain maximum hydration temperature as opposed to 14 hours for

the bagasse soaked in cold water for 48 hours. The equivalent time to attain maximum hydration temperature for neat cement was 6 hours and 7 hours for cement mixed with sand. Using the time to attain maximum hydration temperature parameter alone as measure of compatibility, untreated bagasse could be considered unsuitable, since it took more than 15 h to attain its maximum hydration temperature. Aggregate/cement/water systems that attain maximum hydration temperature in less than 15 h are considered suitable, while those that require more than 20 h are considered inhibitory[7]. The addition of  $\text{CaCl}_2$  at different levels improved the time taken to attain maximum temperature by the mixtures. The best result was obtained with the addition of 2%  $\text{CaCl}_2$ . In this case, the time to attain maximum temperature reduced from 18 h (untreated bagasse) to 7 h (about 62% reduction). A close examination of Table 1 shows that  $\text{CaCl}_2$  was more effective in reducing the time to attain maximum temperature.

### 3.1.2. Maximum Hydration Temperatures of the Mixtures

The maximum hydration temperatures ( $T_{\max}$ ) of the different aggregate-cement mixtures are shown in Table 1. The values ranged from  $40^\circ\text{C}$  for the untreated bagasse/cement/sand mixture to  $66^\circ\text{C}$  for neat cement. Using

$T_{\max}$  as the criterion for compatibility, the cold and hot water treated mixture could be considered unsuitable for cement board production since they reduced hydration temperature to values below  $50^\circ\text{C}$ , the value recommended by [8], and [9]. Addition of 1% and 3%  $\text{CaCl}_2$  however increased  $T_{\max}$  from  $40^\circ\text{C}$  for the untreated bagasse/cement mixture to  $55^\circ\text{C}$  and  $61^\circ\text{C}$  respectively.

$t$  = time to reach maximum temperature

$T_{\max}$  = maximum hydration temperature of the inhibited cement.

$T'_{\max}$  = maximum hydration temperature of the uninhibited cement.

$I$  = inhibitory index

$R$  = hydration rate

$C_t$  = compatibility level based on time to maximum temperature

$CT_{\max}$  = compatibility level based on maximum hydration temperature

$CI$  = compatibility level based on inhibitory index

$CR$  = compatibility level based on hydration rate

$C$  = compatible;  $S$  = suitable;  $U$  = unsuitable;  $IS$  = intermediately suitable;  $MI$  = moderately inhibitory;  $L$  = low;  $M$  = medium;  $H$  = high hydration rate

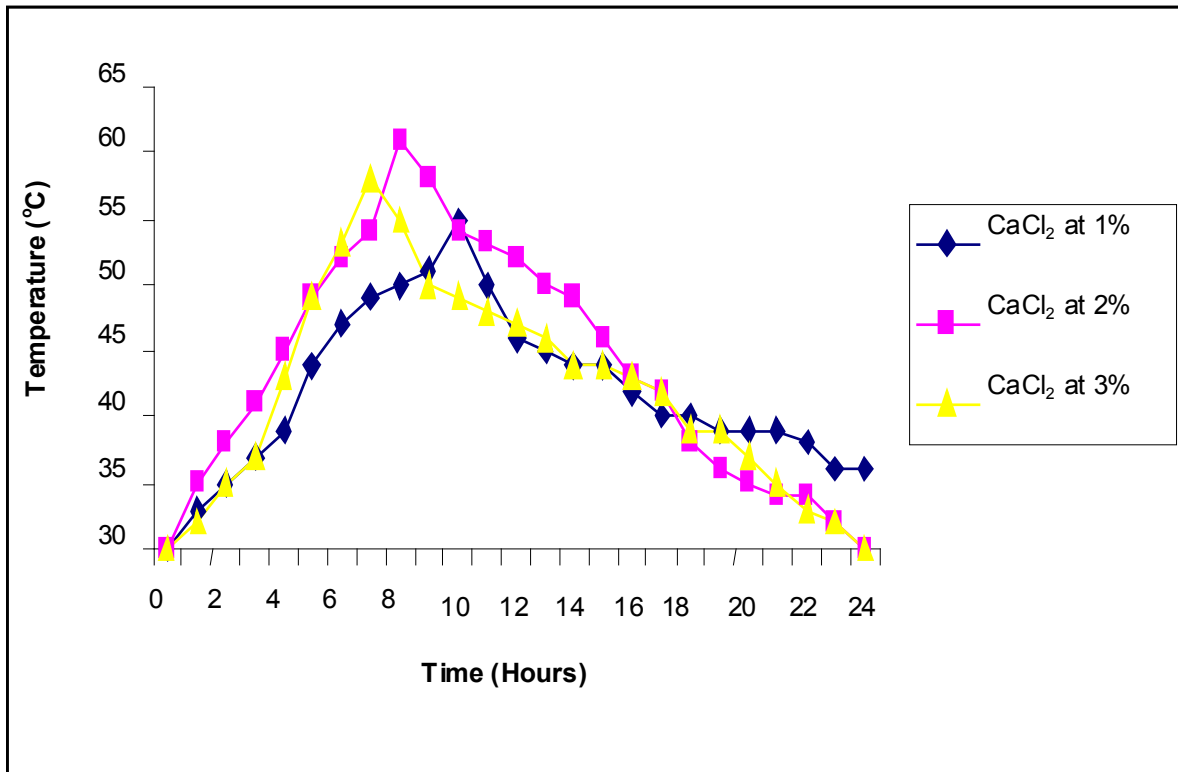


Figure 1. Effects of Chemical Treatments at Different Levels of  $\text{CaCl}_2$  Concentration on Hydration Behaviour of Bagasse Composite

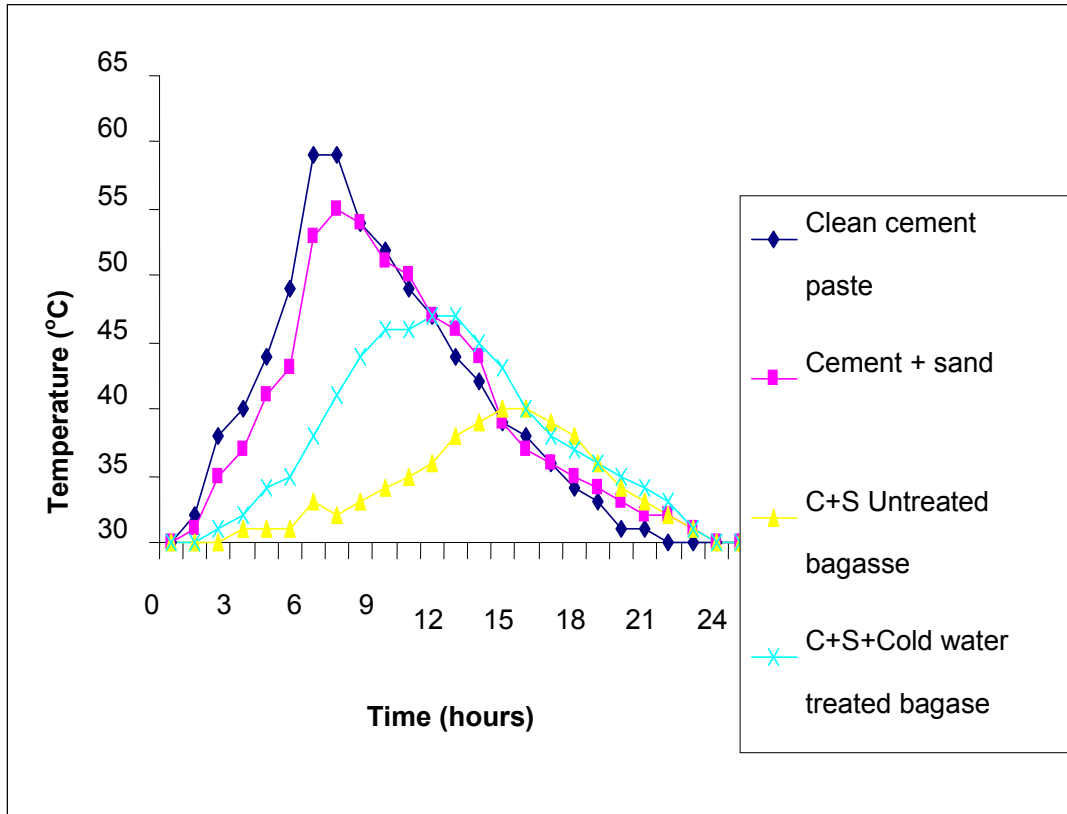


Figure 2. Effects of Cold Water Treatment on Hydration Behaviour of Bagasse Composite

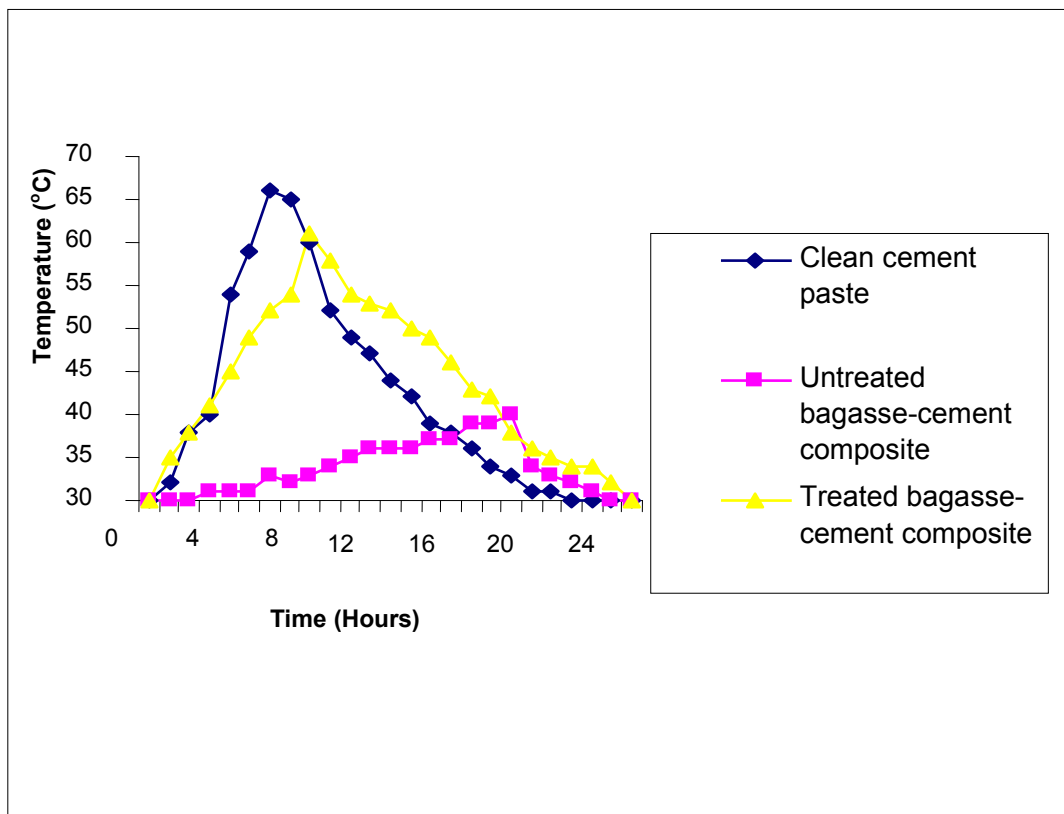


Figure 3. Effects of Chemical Treatment on Hydration Behaviour of Bagasse Composite

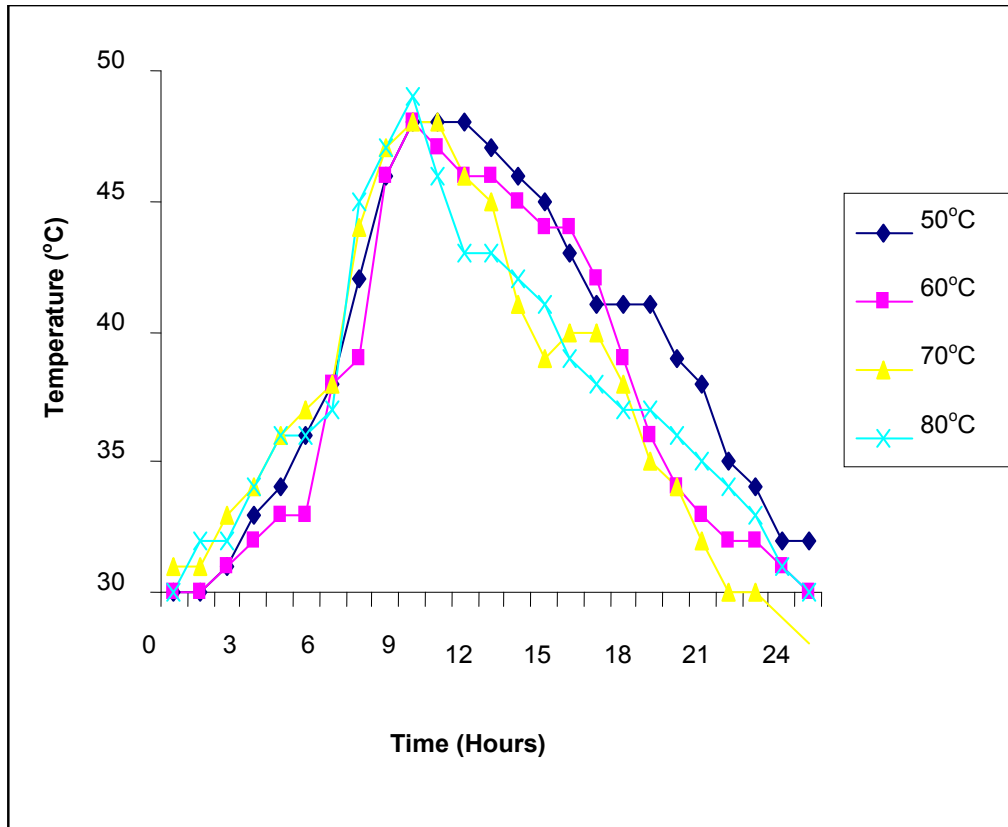


Figure 4. Effects of Hot Water Treatment on Hydration Behaviour of Bagasse Cement Composite

### 3.2. Inhibitory Index

The inhibitory index (I) values for the different treatments are shown in Table 1. The values ranged from 1.58% for bagasse treated with 2%  $\text{CaCl}_2$  to 47.50% for the untreated bagasse cement mixture. The untreated bagasse-cement/sand mixture that had the longest time (18 h) to maximum temperature and lowest hydration temperature value ( $40^\circ\text{C}$ ) also had the highest I value of 47.5% and the least hydration rate of 0.56. These results show that all the different compatibility assessment parameters adopted indicated that the bagasse was incompatible with Portland cement without pre-treatment. Treatment of bagasse with cold water and addition of 2%  $\text{CaCl}_2$  satisfied all requirements for compatibility in terms of time to reach maximum temperature, the maximum hydration temperature and the inhibitory index value. Treatment with  $\text{CaCl}_2$  gave the best result probably due to its capacity to minimize the adverse effect of the soluble sugars and extractives and also to accelerate cement hardening and setting. Comparable data in the literature for the inhibition index of bagasse flakes and particles in cement matrices were not found. Other wood species in mixture with cement that gave moderate inhibition similar to bagasse include *Eucalyptus*[10], *Cypress*[4] and *Pseudoacacia*[8].

**Summary and Conclusion:** Hydration characteristics of bagasse cement composite have been determined. The influence of compatibility based on time, temperatures, hydration index and rate were examined for different

treatments. It was concluded that bagasse treated with  $\text{CaCl}_2$  at 2% is compatible with ordinary Portland cement.

The following conclusions were drawn from the hydration test;

1. Untreated bagasse is not compatible with ordinary Portland cement.
2. Addition of 2%  $\text{CaCl}_2$  improved the temperature and reduced the setting time.
3. Addition of 2%  $\text{CaCl}_2$  also gave the least inhibitory index and the highest hydration rate.

This showed that when bagasse cement composite is treated with 2%  $\text{CaCl}_2$  the result is compatible and suitable for construction purposes.

## REFERENCES

- [1] Olorunnisola, A.O. Pitman, A. and Mansfield-William H. (2005). Strength Properties and Potential Uses of Rattan-Cement Composites. *Journal of Bamboo and Rattan* Vol. 4 (4) pp. 343 – 352.
- [2] Olorunnisola, A.O. Pitman, A. and Mansfield-William H. (2005). Hydration Characteristics of Cement-bonded Composites made from Rattan Cane and Coconut Husk. *Journal of Bamboo and Rattan*, 4 (2) pp. 193-201.
- [3] Hofstrand, A.D.; Moslemi, A.A.; Garcia, J.F. (1984). Curing characteristics of wood particles from nikne northern Rocky Mountain Species mixed with Portland cement. *Forest*

Products Journal 34 (2) : 57 – 61.

- [4] Okino, E.Y.A.; De Souza, M.R.; Santana, M.A.E.; Da Alves, M.V.; De Souza, M.E.; Teixeira, D.E. (2005). Physico-mechanical Properties and Decay Resistance Of *Cupressus ssp* Cement-Bonded Particleboards. *Cement and Concrete Composites* 27: pp. 333 – 338.
- [5] Moslemi, A.A. Garcia, J.F. and Hofstrand, A.D. (1983): An Evaluation of the rate of Heat Evolution of Portland Cement – Northern Rocky Mountain spp. *Wood Fibre and Science* 15(2). 164-176.
- [6] Papadopoulos, A.N. (2007). An Investigation of the Suitability of Some Greek Wood Species in Wood Cement Composites Manufacture. *Springer Vertage Holz Roh Werkst* (2007) 65 (245-246).
- [7] Papadopoulos, A.N. (2008). Natural Durability and Performance of Hornbeam Cement Bonded Particleboard. *Maderas Ciencia tecnologia*, 10 (2) 93 – 98.
- [8] Semple, K.E. and Evans, P.D. (2004). Wood-Cement Composites – Suitability of Western Australian Mallee Eucalypt, Blue Gum and Melaleucas. A Report for the RIRDC/Land and Water Australia/FWPRDC/MDBC Joint Venture Agroforestry Program.
- [9] Wei, Y.M.; Zhou, Y.G. and Tomita, B. (2000). Study of Hydration Behaviour of Wood Cement-based Composite II: Effect of Chemical Additives on the Hydration Characteristics and Strengths of Wood-Cement Composites. *The Japan Wood Research Society Journal*, Vol. 46 (2000) pp. 444 – 451.
- [10] Okino, E.Y.A.; De Souza, M.R.; Santana, M.A.E.; Da Alves, M.V.; De Souza, M.E.; Teixeira, D.E. (2004). Cement-Bonded wood Particleboard with a mixture of eucalypt and rubberwood. *Cement and Concrete Composites* 26: pp. 729 – 734.